

A simplified measurement method for the determination of impact sound reduction

Marc Sommerfeld

Physikalisch-Technische Bundesanstalt, 38116 Braunschweig, Germany, marc.p.sommerfeld@ptb.de

Introduction

The impact sound reduction is the main quantity for describing the acoustic behaviour of floor coverings. Its determination is standardised in ISO 140-8 [4] and ISO 140-11 [5] and requires the use of a special test facility. This facility consists of two rooms of about 50 m³ each separated by a 14 cm concrete slab or a special timber joist floor. Manufacturers of floor coverings see the advantage of having own test facilities but the investment can often not be afforded by the small and medium size enterprises. Therefore, a research project was started with the aim to reduce the effort for the determination of the impact sound reduction. The project is funded by the German Federation of Industrial Research Associations "Otto von Guericke" Inc. (AiF) and has a duration of 2.5 years. The research work is carried out at Physikalisch-Technische Bundesanstalt (PTB) and at the Research Institute of Leather and Plastic Sheetting gGmbH (FiLK).

Existing short test method

Starting point for the investigation is a known short test method TGL [1], [2]. The maximum acceleration of a 500-g-hammer is measured when it falls from a height of 4 cm on a soft layer. From the maximum acceleration, the rated value of the reduction of transmitted impact noise is calculated directly.

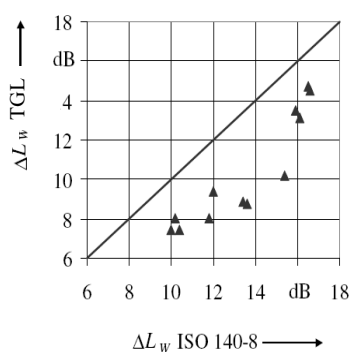


Figure 1: Difference of ΔL_w [dB], concrete: TGL [2] vs. ISO procedure [4]

Initially it was examined whether this procedure, perhaps with small adaptations, can also be applied in today's time. It has appeared, in an AiF-preproject [3] that the results of the TGL procedure are systematically about 3 dB smaller than those of the ISO procedure (see figure 1). Based on this situation, the TGL procedure was analysed. The assumption of an impulse-shape from which a general spectrum was

derived (for the reduction of transmitted impact noise) turned out to be essential. Moreover, a typical value of the size of the impulse is used which was determined from measurements [1] with floor coverings available at that time. An adaptation to today's layers would not lead to the goal, because the measuring procedure would not be applicable without necessary adjustments at regular intervals in comparison to the floor coverings currently placed on the market. A project task is the elaboration of a procedure which can be introduced as a work item proposal at ISO. This aim is not accessible by the (perpetual) modification of the TGL-standard.

New compact measurement setup - COMET

Within the scope, a compact measurement setup is developed which delivers rated values [6] of the reduction of transmitted impact noise. The results should correspond on average to those of the ISO procedure ISO 140-8 [4] respectively ISO 140-11 [5] and the realisation of the measurement should be easy. In the constructional systems, two floors should be used by analogy with the ISO procedure: a heavyweight floor and a lightweight floor. The required applicability is the operation with soft floor coverings, parquet or laminate is to be examined.

The first construction consists of a concrete slab of the dimension 1.2 m x 0.8 m x 0.2 m which lies in a steel rack in the euro-format. Between stilts and concrete slab, an elastic material is introduced which decouples the concrete slab. The system resonance lies at $f = 27$ Hz and therefore below the interesting frequency range of building acoustics (see figure 2).

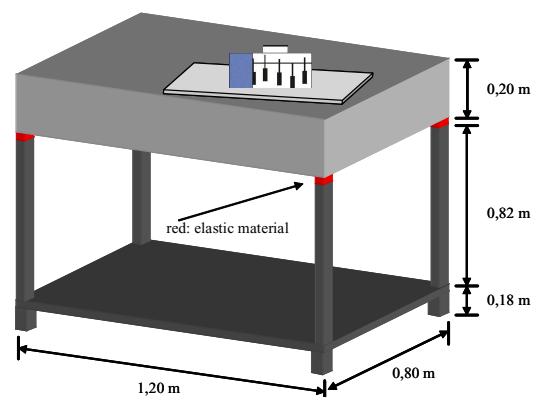


Figure 2: Construction of COMET, concrete floor

The second construction consists of a timber joist floor of the dimension 1.2 m x 0.8 m x 0.2 m which lies in a steel rack in the euro-format (see figure 3). Between stilts and

concrete slab an elastic material is introduced which decouples the timber floor with a resonance at $f=22$ Hz. It is thus below the interesting frequency range of building acoustics. The construction is related to the timber joist floor (type 1) described in ISO 140-11. The only difference in dimension is the distance between the two timber joists: instead of 62.5 cm they have a gap of 68 cm.

The measurements are carried out with a 1/3-octave band analyser. For the excitation, an ISO tapping machine is used. In analogy to the ISO procedures, two tests are performed, once with and once without the floor covering on the concrete. At the bottom of the concrete slab, the appearing oscillations are measured with six accelerometers and the impact noise reduction has to be averaged over those receiver points. The figures 4, 5, 7 and 8 show the results of this step.

The positions of the receivers are randomly distributed and not arranged in symmetric lines. From two measurements (with/without layer) one calculates the impact noise reduction:

$$\Delta L = L_{an,0} - L_{an} \quad (1)$$

where: $L_{an,0}$ is the averaged acceleration level at the bottom of the concrete slab without covering and L_{an} the same measured quantity with covering.

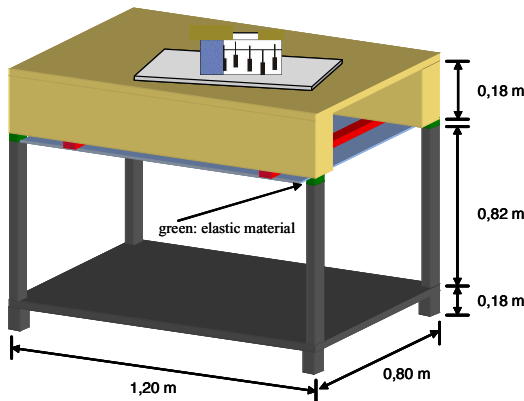


Figure 3: Construction of COMET, timber floor

Afterwards ΔL can be rated according to ISO 717-2 [6]. The result is the rated reduction of transmitted impact noise ΔL_w in dB. The figures 6 and 9 show the results of this step. It is possible to generate other rated values from ΔL . This is an advantage compared to the TGL procedure with which only ΔL_w could be determined.

Results – heavyweight floor

The results of the new compact method are compared to those of the ISO procedure. The figures 4 and 5 show two by two measurements each of ΔL .

The colours stand for different coverings. The deeper colour is correlated with the compact - the lighter with the ISO procedure: black belongs to PVC, green to carpet, blue to linoleum and red to laminate.

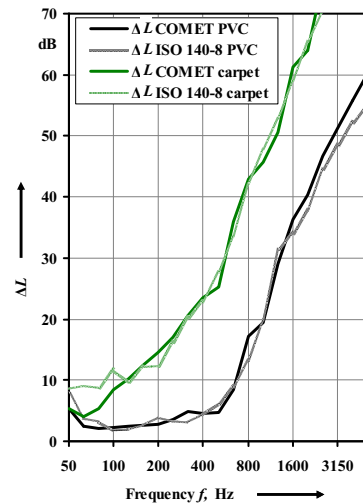


Figure 4: Impact noise reduction ΔL [dB], concrete: COMET vs. ISO procedure

It is to be recognised that spectral divergences hardly exist between the compact and ISO procedure for PVC, carpet and linoleum coverings due to their local elastic effect. The curves nearly fit. Laminate reveals larger discrepancies due to its plate-like effect. The compact procedure delivers lower values compared to ISO in this case.

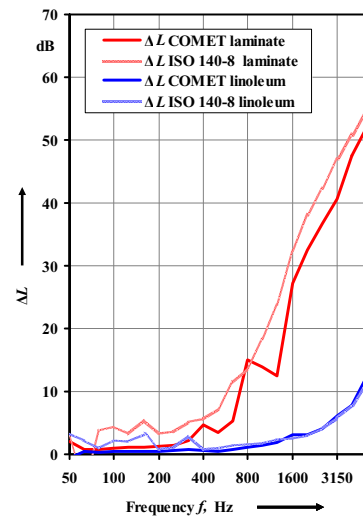


Figure 5: Impact noise reduction ΔL [dB], concrete: COMET vs. ISO procedure

Figure 6 shows the results of impact noise reduction ΔL_w determined by the compact and ISO procedure. Altogether 25 PVC, 7 carpet, one laminate and one linoleum floor covering were tested. The diagram shows that no systematic deviation is visible between both measuring procedures. The mean squared deviation msd

$$msd = \sqrt{\frac{1}{(N-1)} * \sum_{i,j=1}^N (\Delta L_{w,i,Comet} - \Delta L_{w,j,ISO})^2} \quad (2)$$

of all 34 measurements is 0.8 dB.

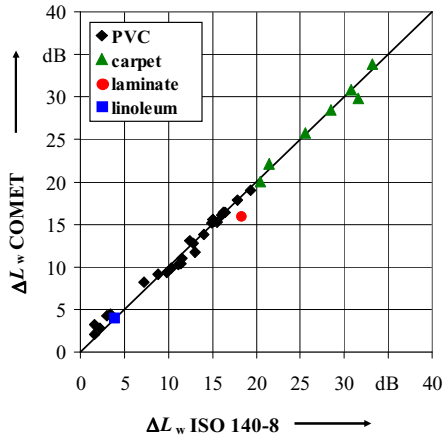


Figure 6: Deviation of ΔL_w [dB], concrete: COMET vs. ISO procedure

Table 1 shows the maximum deviation Δ_{max} .

$$\Delta_{max} = |\Delta L_w, compact - \Delta L_w, ISO|_{max} \quad (3)$$

The largest deviation is yielded for the laminate due to the different spectral results (figure 5). Nevertheless, all deviations are relatively small in view of the usual uncertainties in building acoustics which often reach values of several dB.

Floor Covering	Δ_{max}
PVC	1.6
Carpet	1.8
Laminate	2.4
Linoleum	0.1

Table 1: Maximum deviation Δ_{max} , concrete

Results – lightweight floor

The measured data is presented in the same way as for the heavyweight floor. Figure 7 and 8 show two pairs of measurements: PVC / carpet and laminate / linoleum floor covering. The compact procedure delivers lower values for the PVC / laminate and larger ones for the carpet / linoleum compared to ISO in these cases.

A comparison between the impact noise reductions determined by the compact and the ISO procedure is shown in figure 9. Altogether 13 PVC, 7 carpet, one laminate and one linoleum floor covering were tested.

Table 2 shows the maximum deviation Δ_{max} .

Floor Covering	Δ_{max}
PVC	1.7
Carpet	4.4
Laminate	2.8
Linoleum	0.7

Table 2: Maximum deviation Δ_{max} , timber

They reach values of up to 4.4 dB. The discrepancies are to be investigated in future.

There is no systematic deviation between the results visible. The mean squared deviation turns out to be 1.9 dB. It is thus larger than for the concrete slab. The reason is the more complex transfer of vibrational energy to the measuring points due to the inhomogeneous receiving structure.

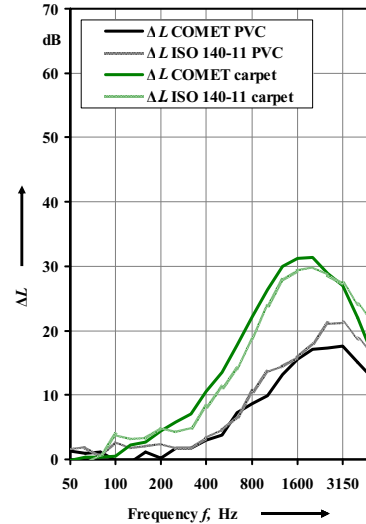


Figure 7: Impact noise reduction ΔL [dB], timber: COMET vs. ISO procedure

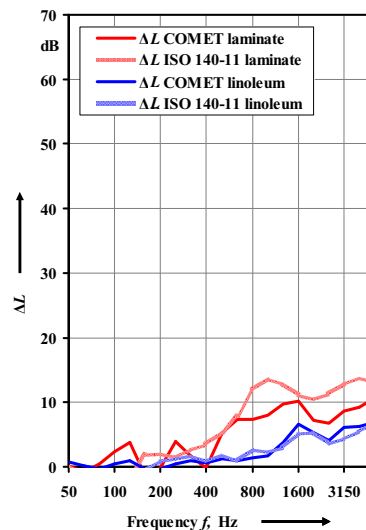


Figure 8: Impact noise reduction ΔL [dB], timber: COMET vs. ISO procedure

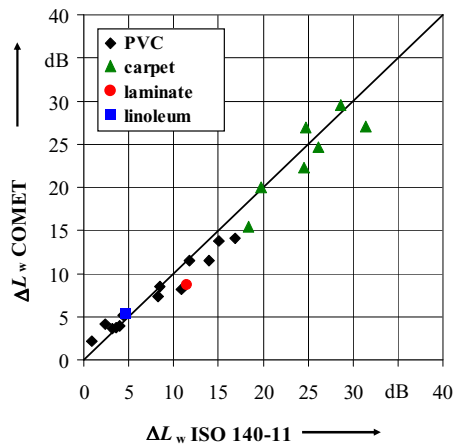


Figure 9: Deviation of ΔL_w [dB], timber: COMET vs. ISO procedure



Figure 10: Construction of COMET, concrete floor

Summary

A new compact measurement setup was developed which can be used without adaptation and provides good results, low effort, easy handling and therefore fulfils the requirements. The basic idea consists in substituting the measurement of the sound pressure in 1/3-octave bands in the receiving room to the measurement of the acceleration levels in 1/3-octave bands at the bottom of a massive concrete slab or timber joist floor. The relatively low deviations between the results obtained by the COMET and ISO procedure are the results of the similarity between these two procedures. To understand the larger deviations for the timber joist floor and for the laminate, a comprehensive model of the whole measurement procedure will be developed in the future. It will especially be investigated under what circumstances the results of the COMET - and ISO procedure are in good agreement.

Acknowledgements

The author expresses his gratitude to AiF for funding the project and to the manufacturers of floor coverings who supplied numerous test specimens. The contribution of FiLK, especially in establishing the contact to AiF and to industry, is gratefully acknowledged. I furthermore thank Prof. Dr.-Ing. Werner Scholl and Dr.-Ing. Volker Wittstock for initiating the project and for their enduring support. Many thanks go to Dipl.-Ing. Sylvia Stange-Kölling for doing numerous measurements.



Figure 11: Construction of COMET, timber floor

References

- [1] E. Sonntag: Kurzprüfverfahren für das Verbesserungsmaß des Trittschallschutzes bei Weichbelägen, Bauakademie der DDR (1977) [in German]
- [2] TGL 10688/13: Messverfahren der Akustik – Bestimmung des Trittschallverbesserungsmaßes von Weichbelägen mit Kurzprüfverfahren, DDR (1987) [in German]
- [3] C. Bethke: Überprüfung des vereinfachten Verfahrens nach TGL 10688/13 zur Bestimmung des Trittschallverbesserungsmaßes von Bodenbelägen, PTB Report (2004) [in German]
- [4] ISO 140-8: Acoustics – Measurement of sound insulation in buildings and of building elements (Part 8: Laboratory measurements of the reduction of transmitted impact noise by floor coverings on a heavyweight standard floor), CEN (1995)
- [5] ISO 140-11: Acoustics – Measurement of sound insulation in buildings and of building elements (Part 11: Laboratory measurements of the reduction of transmitted impact sound by floor coverings on lightweight reference floors), CEN (1995)
- [6] ISO 717-2: Acoustics – Rating of sound insulation in buildings and of building elements (Part 2: Impact sound insulation), CEN (2004)